

# Fabrication, characterization, and microscopic imaging of Fe<sub>2</sub>O<sub>3</sub>-modified electrospun nanofibers

Mohammad Amin Pordel<sup>1</sup>, Afshin Maleki<sup>2,✉</sup>, Mehrdad Khamforosh<sup>3</sup>, Hiua Daraei<sup>2</sup>, Reza Rezaee<sup>2</sup>, Saeed Dehestani<sup>2</sup>

1. Student Research Committee, Kurdistan University of Medical Sciences, Sanandaj, Iran
2. Department of Environmental Health Engineering, Environmental Health Research Center, Kurdistan University of Medical Sciences, Sanandaj, Iran
3. Department of Chemical Engineering, Faculty of Engineering, University of Kurdistan, Sanandaj, Iran

**Date of submission:** 12 Mar 2017, **Date of acceptance:** 25 Sep 2017

## ABSTRACT

This study explored the fabrication, characterization, and microscopic imaging of highly porous electrospun nanofibers based on pure and Fe<sub>2</sub>O<sub>3</sub> nanoparticle modified polyacrylonitrile (PAN) fibers. The desired electrospinning mixture comprising polymer and nanoparticles in dimethyleformamide, was prepared. During electrospinning, the precursor solution was injected using a syringe pump. The empirical parameter influences, including nanoparticles dose, polymer weight percentage, and thickness as applied polymer syringe, were studied on the product morphology and uniformity. The products were analyzed by Fourier transform infrared (FT-IR) spectrophotometer, scanning electron microscopy (SEM), and X-ray diffraction (XRD). The results demonstrate that changes in the investigated empirical parameters cause fiber morphology variations and uniformity. Therefore, a strong interaction exists between Fe<sub>2</sub>O<sub>3</sub> and PAN. In general, addition of nanoparticles to PAN solution resulted in a decrease in the average fiber diameter compared to pure PAN.

**Keywords:** Electrospun, nanofibrous, PAN, Fe<sub>2</sub>O<sub>3</sub>

## Introduction

In general, fibers are divided in three groups comprising microfibers, nanofibers, and moderate fibers. The nanofibers include three important types of polymeric, mineral, and carbon nanofibers.<sup>1</sup> This study used polymeric nanofibers due to their importance in fabricating the nanofibers. Several methods are reported to fabricate nanofibers, such as phase separation, drawing, templates, selfassembly, and electrospinning.<sup>2</sup> Electrospinning process has attracted immense attention since its first report in 1934.<sup>3</sup> The electrospinning of various polymers is an internationally highly recognized method used to fabricate the polymeric nanofibers of nanosized diameter and for a broad range of complex architectures of nanofibers.<sup>4-9</sup> This technology has several

applications in the medical field, namely tissue engineering, equipment and medical implants, medical masks, and drug delivery, and also in other fields where composites reinforced with the layers of nanofibers are used in filtration, water and wastewater treatment, and ion-exchange membranes.<sup>4-10</sup> Moreover, it is used to magnificate a variety of hybrid nanofibers by incorporating the nanomaterials into several polymer matrices. The nanofibers produced by electrospinning method reveal several significant advantages: small diameter (50 nm–10 μm), high aspect ratio (the ratio of length to diameter), large specific area (surface area to volume ratio), variety in composition, unique physicochemical properties, and design flexibility for physical/chemical surface functionalization.<sup>11-13</sup> Long nanofiber with controllable morphology can produce continuously by electrospinning technique.<sup>14</sup> During electrospinning, a high voltage supply is applied for jet formation in the polymeric solution at the needle tip. The unwoven nanofibers gather on the collector.<sup>15</sup> Nanofiber

✉ Afshin Maleki  
maleki43@yahoo.com

**Citation:** Pordel MA, Maleki A, Khamforosh M, Daraei H, Rezaee R, Dehestani S. Fabrication, characterization, and microscopic imaging of Fe<sub>2</sub>O<sub>3</sub>-modified electrospun nanofibers. J Adv Environ Health Res 2017; 5(3): 146-153

membranes with several properties including small pore size, high permeability, high porosity, and interconnected pores form a good alternative for filtration purposes.<sup>16-17</sup> In this study, pure PAN fibers and PAN fibers modified with various percentages of Fe<sub>2</sub>O<sub>3</sub><sup>18</sup> nanoparticle loadings have been fabricated via an electrospinning process. Optimum conditions (weight percentage of polymer and Fe<sub>2</sub>O<sub>3</sub> nanoparticles dose) to achieve bead-free fibers with several characteristics, in particular nanoparticle loadings, are explored. The surface morphology of the PAN fiber and PAN fiber modified with various percentages of Fe<sub>2</sub>O<sub>3</sub> nanoparticles are characterized by several techniques, including Fourier transform infrared (FT-IR) spectroscopy, scanning electron microscopy (SEM), and X-ray diffraction (XRD).

## Materials and Methods

### Materials

Polyacrylonitrile (PAN, MW = 100,000) was purchased from Polyacryl Iran Corporation (Iran), *N,N*-dimethylformamide (DMF, 99.9%) was purchased from Merck (Iran), and for the synthesis of Fe<sub>2</sub>O<sub>3</sub> nanoparticles by sol-gel method, salt ferric chloride (FeCl<sub>3</sub>) and sodium hydroxide (NaOH) were used from Merck.

### Fabrication of pure casting solution and nanosized fibers

#### Polymeric solution preparation

The casting solution involved PAN/DMF with polymer loading of 8.0, 10.0, 12.0, and 14 wt% was prepared. A specific amount of Fe<sub>2</sub>O<sub>3</sub> nanoparticles (0.01, 0.1, and 1.0 wt%) was added into the casting solutions. Ultrasonication was performed for 45 min to disperse the Fe<sub>2</sub>O<sub>3</sub> nanoparticles within the solutions at room temperature. Both the pure casting solutions and the nanoparticle modified solutions were used for electrospinning fibers and subsequent morphological investigation.

#### Fabrication of nanosized fibers

Both pure and PAN/Fe<sub>2</sub>O<sub>3</sub> nanosized fibers were prepared using the electrospinning method. The viscous polymeric solutions were

loaded in a 1 ml syringe equipped with a stainless steel gauge 25 needle. The needle was connected to the positive pole of a high voltage power supply, generating a DC voltage up to 20 kV. The formed polymeric fibers were collected on a rotating cylindrical collector after solvent evaporation. The solution was constantly and controllably supplied using a syringe pump (STC-527, Korea). The volume rate of the polymeric solution was controlled at 23 ml/min. In this study, the applied voltage was adjusted in the range of 16–18 kV. An external electric field with a high voltage applied to the polymer solution through the positive electrode can overcome the surface tension of the viscous polymer solution and form a polymer jet, which is accelerated toward the collector and forms the fibers.

### Characterization

The surface morphology of the electrospun pure nanofiber and the one modified by Fe<sub>2</sub>O<sub>3</sub> nanoparticles, was studied with the SEM (TSCAN, Czech). The intact samples were coated with gold for SEM observation. In the SEM photos, the nanofiber average diameters were evaluated using Digimizer.v4.1.1.0 software and the results were presented as the average diameter ± standard deviation. Fourier transform infrared spectroscopy (FT-IR Tensor 27, Bruker Optics, Germany) was used between 1000 and 4000 cm<sup>-1</sup>, in the absorption mode, with 4 cm<sup>-1</sup> of resolution. The crystal structure of the pure PAN nanofiber and the nanofiber modified with Fe<sub>2</sub>O<sub>3</sub> nanoparticles was characterized using an X-ray diffraction (Inel, France) with Cu K $\alpha$  ( $\lambda = 1.5405 \text{ \AA}$ ) radiation over the  $2\theta$  range of 0–80°.

## Results and discussion

### PAN concentration effect

The bead formation during electrospinning process affects the properties of the electrospun fibers and results in several issues, such as a decreased specific surface area.<sup>5,19</sup> Hence, in this research, several PAN concentrations used to investigate the effect of the concentration on beads formation at the process include: 8, 10, 12, and 14 wt%. Figure 1 presents the SEM of

the pure PAN nanofibers with 8, 10, 12, and 14 wt% polymer in the casting solution, respectively. As observed in Figure 1, the beads may form on the surface of the fibers at low concentrations. Polymeric solutions involved 8 wt% polymer loading results in the fibers along with beads, (Fig. 1A); however, almost uniform PAN nanofibers with few beads were obtained at 10 wt% PAN casting solution, (Fig. 1B). On increasing the polymer concentration to 12 wt%, the fibers become more uniform, smooth, and lack nodes. Nevertheless, at 14 wt% concentration, a little nonuniformity is observed on the surface of the fibers. It could be a result of the increasing concentration of the polymer, which increases the mass and the diameter of the

nanofibers in jet spinning. Thus, the polymer chains are strongly held due to the increase in viscosity. Therefore, the fibers stretch more. An optimum concentration exists to achieve uniform fibers without beads. It was observed that increasing the concentration of the polymer results in less beads formation. Hence, 12.0 wt% polymeric solution was chosen for this study. Moreover, the diameter distribution of the nanofibers is presented in Figure 2. In general, the diameter of the nanofibers varies from 190 to 211 nm. The average diameter of the nanofibers including 8, 10, 12, and 14 wt% PAN was 211.03, 205.82, 190.76, and 196.76 nm, respectively. A falling trend of the average diameter was observed from 8 to 12 wt% casting

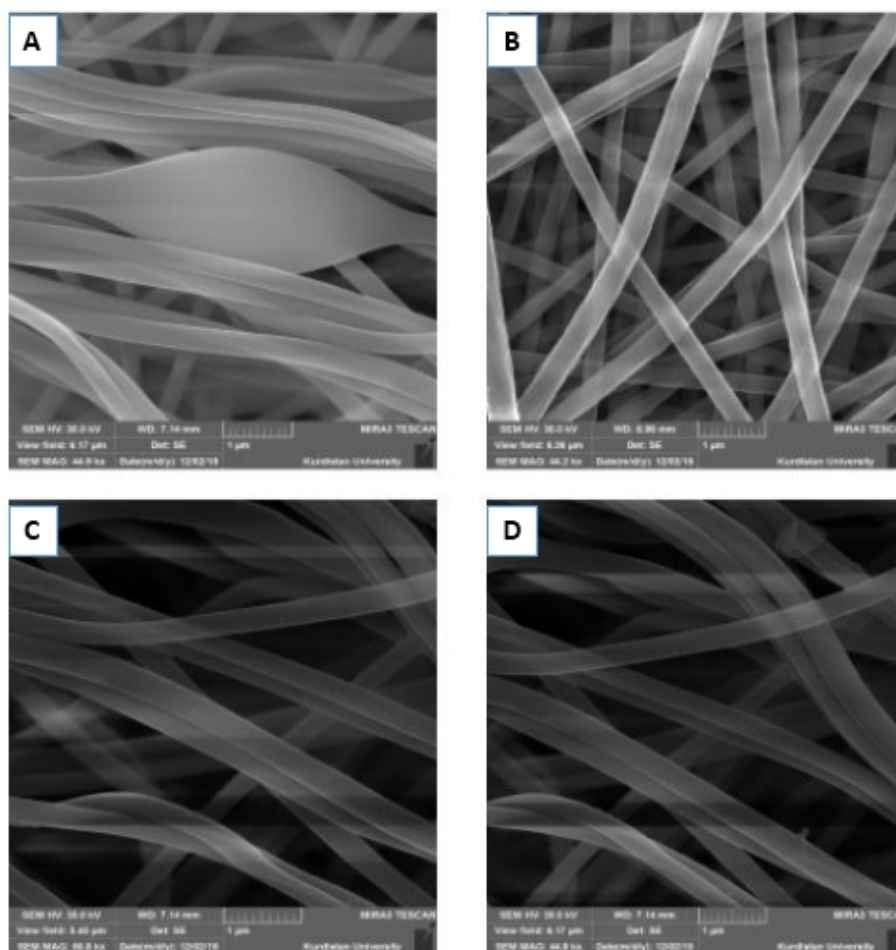


Fig. 1. SEM images of pure PAN nanofibers with a PAN loading (A) 8 wt%, (B) 10 wt%, (C) 12 wt%, and (D) 14 wt%.

solution, but after that the average diameter was increased. Uniform pure nanofibers (12.0 wt%

PAN) were obtained with an average diameter of about 190.76 nm. The more concentrated

polymeric solution, the more viscosity and less evaporation. It could be expected that the nanofibers with more thickness were obtained due to higher concentration of the polymer.

Therefore, the diameter of the nanofibers could change due to the varying polymer

concentration, as presented in Figure 2. Several parameters including electrostatic repulsion, surface tension, and viscoelastic force, are essential in controlling the fiber quality during electrospinning.<sup>5,20,21</sup>

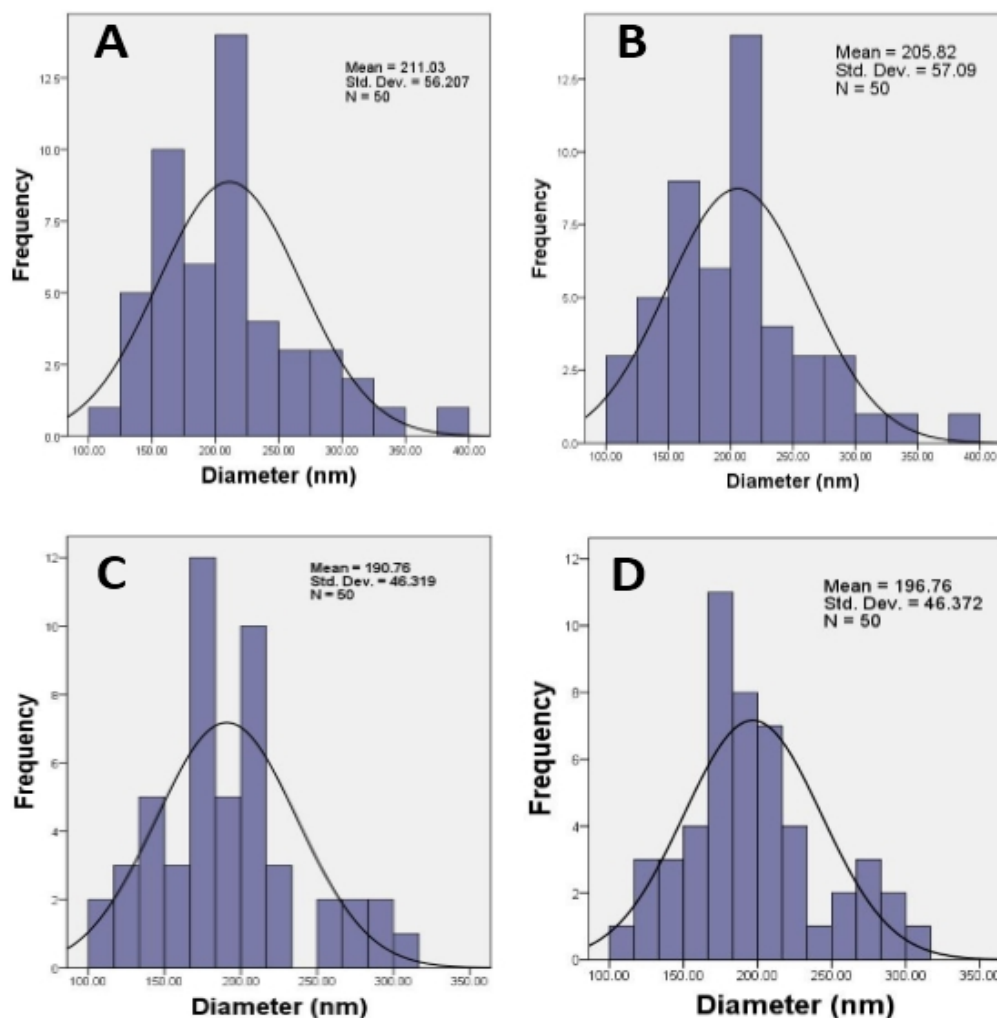


Fig. 2. Diameter distribution of pure PAN nanofibers with loadings (A) 8 wt%, (B) 10 wt%, (C) 12 wt%, and (D) 14 wt%.

### ***Effect of Fe<sub>2</sub>O<sub>3</sub> nanoparticles on the fiber morphology***

Modified Fe<sub>2</sub>O<sub>3</sub>-nanofibers with distinct nanoparticle loadings (0.01, 0.1, 1 wt%) were fabricated (Fig. 3). The variation in the nanoparticle concentration due to weight affects the several features of the fibers; however, the of the agglomeration of Fe<sub>2</sub>O<sub>3</sub> particles increased. This affects the physical characteristics of the nanofibers.

The morphological features of Fe<sub>2</sub>O<sub>3</sub> nanoparticles are presented in Figure 4

challenges such as particles dispersion and agglomeration were encountered during electrospinning, when the loading of the Fe<sub>2</sub>O<sub>3</sub> nanoparticle was increased. An efficient dispersion was achieved in lower loadings such as 0.01 and 0.1 wt%, whereas when Fe<sub>2</sub>O<sub>3</sub> loading was raised up to 1 wt%, the possibility indicating porous nanosized particles with a little homogeneous and polygonal structure.

The addition of nanoparticles within the polymeric solution increases the mechanical strength of the fibers and creates nanopores

within the nanofibers.<sup>21</sup> Moreover, the structural modification with Fe<sub>2</sub>O<sub>3</sub> nanoparticles enhances

the strength and uniformity of the nanofibers.

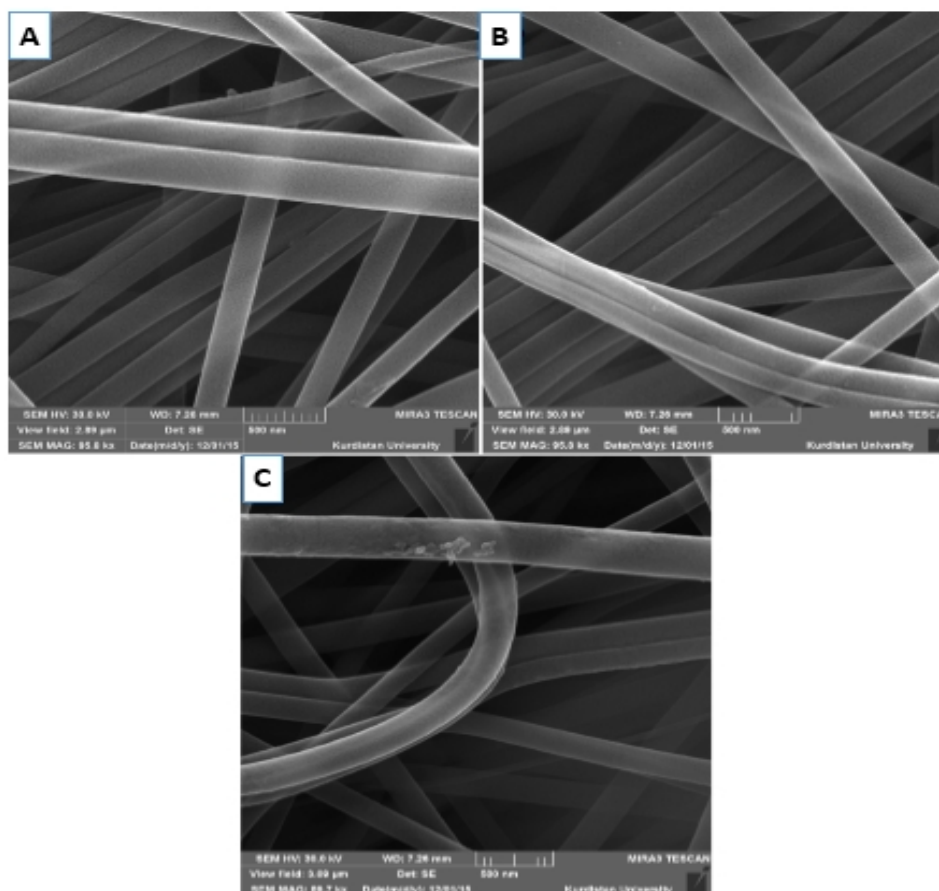


Fig. 3. The effect of nanoparticle loadings (A) 0.01 wt%, (B) 0.1 wt%, and (C) 1 wt% on the morphological features of the nanofibers

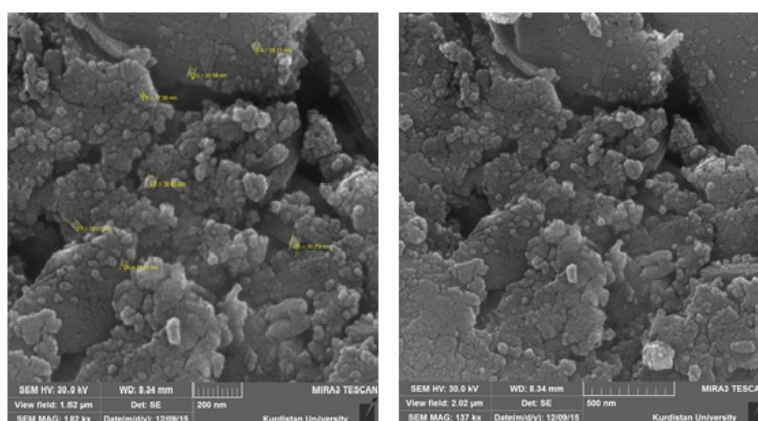


Fig. 4. SEM images of Fe<sub>2</sub>O<sub>3</sub> nanoparticles

### FT-IR spectra

Figure 5 presents the FT-IR spectra recorded in the spectral range of 1000–3500 cm<sup>-1</sup> of the as-received PAN powder, pure PAN fibers, and nanofibers with 0.1 wt%,

respectively. The peak at around 2931 cm<sup>-1</sup> is assigned to the stretching vibration of the methylene (–CH<sub>2</sub>–) group and at 2243 cm<sup>-1</sup> and 1452 cm<sup>-1</sup> is assigned to the stretching vibration of nitrile groups (–CN–) and the bending



vibration of methylene ( $-\text{CH}_2-$ ), respectively.<sup>21</sup> The peaks at around  $1235\text{ cm}^{-1}$  and  $1094\text{ cm}^{-1}$

correspond to the stretching carbonyl group in the aliphatic amines.<sup>21-22</sup>

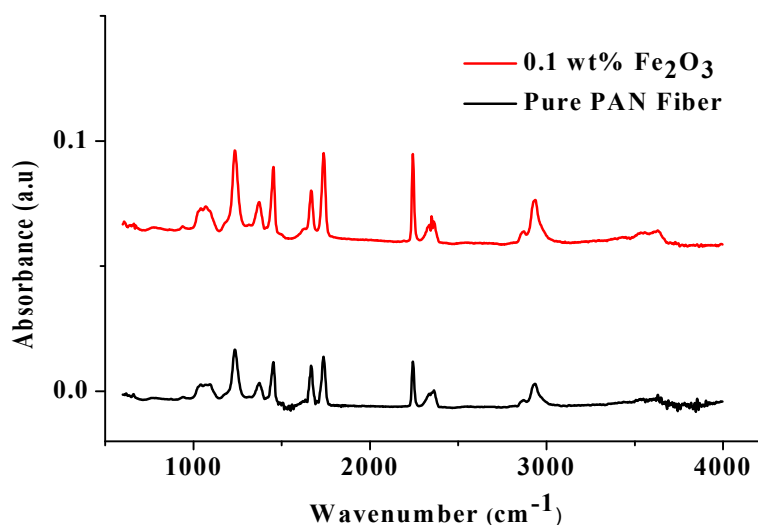


Fig. 5. FT-IR spectra of pure PAN fibers and PAN/ $\text{Fe}_2\text{O}_3$  nanocomposite fibers with 1 wt%  $\text{Fe}_2\text{O}_3$  nanoparticle

### XRD

The crystalline properties of nanofibers in the electrospinning processes are essential when the materials are designed and fabricated for commercial purposes.<sup>23</sup> In order to investigate the crystalline structure of the iron oxide

modified nanofibers in electrospinning, XRD measurements were performed.<sup>21</sup> Figure 6 presents the XRD patterns of the electrospun pure PAN fibers and the PAN/ $\text{Fe}_2\text{O}_3$  nanofibers involved in 0.1 wt%  $\text{Fe}_2\text{O}_3$  loading.

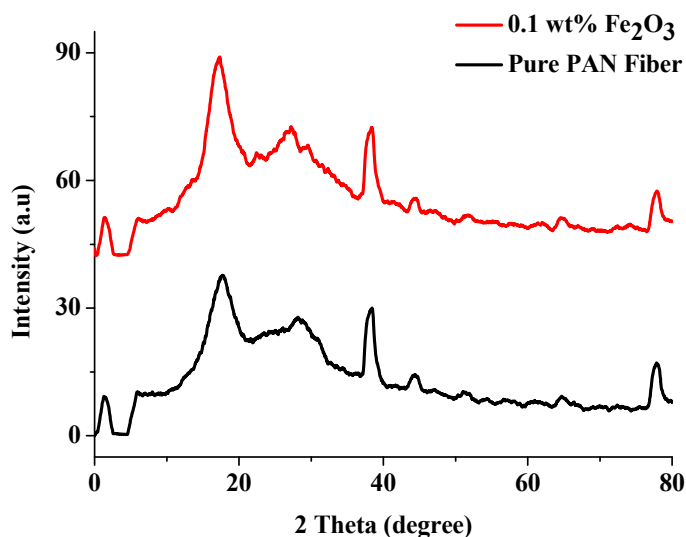


Fig. 6. XRD patterns of pure PAN fibers and PAN/ $\text{Fe}_2\text{O}_3$  nanocomposite fibers with 1 wt%  $\text{Fe}_2\text{O}_3$  nanoparticle

### Conclusion

Pure and modified PAN fibers by  $\text{Fe}_2\text{O}_3$  were prepared by the electrospinning process. The results indicated that both the polymer and

nanoparticles concentration have significant effects on the fiber morphology. SEM analysis revealed that uniform bead-free nanofibers could be fabricated over 10 wt% PAN

concentration. The beads could be effectively minimized by increasing the polymer concentration. XRD and FT-IR results indicated that the addition of Fe<sub>2</sub>O<sub>3</sub> nanoparticles reveals a significant impact on the PAN crystallization structure and the changing diameter of fibers. Hence, there is a strong interaction between Fe<sub>2</sub>O<sub>3</sub> and PAN. In general, the addition of nanoparticles to PAN solution resulted in a decrease in the average diameter of modified fibers compared to the pure ones.

### Acknowledgments

The authors would like to express their gratitude toward the Kurdistan University of Medical Sciences, Iran, for funding this research.

### References

- Ahmed FE, Lalia BS, Hashaikeh R. A review on electrospinning for membrane fabrication: challenges and applications. *Desalination*. 2015;356:15-30.
- Ramakrishna S, Fujihara K, Teo W-E, Lim T-CH, Ma Z. Basics Relevant to Electrospinning, in *An Introduction to Electrospinning and Nanofibers*. Singapore. World Scientific Publishing Co. Pte. Ltd.;2005
- Li D, Babel A, Jenekhe SA, Xia Y. Nanofibers of conjugated polymers prepared by electrospinning with a two-capillary spinneret. *Advanced Materials*. 2004;16(22):2062-6.
- Huang Z-M, Zhang Y-Z, Kotaki M, Ramakrishna S. A review on polymer nanofibers by electrospinning and their applications in nanocomposites. *Composites science and technology*. 2003;63(15):2223-53.
- Li D, Xia Y. Electrospinning of nanofibers: reinventing the wheel? *Advanced materials*. 2004;16(14):1151-70.
- Greiner A, Wendorff JH. Electrospinning: a fascinating method for the preparation of ultrathin fibers. *Angewandte Chemie International Edition*. 2007;46(30):5670-703.
- Reneker D, Yarin A, Zussman E, Xu H. Electrospinning of nanofibers from polymer solutions and melts. *Advances in applied mechanics*. 2007;41:43-346.
- Greiner A, Wendorff J. Functional self-assembled nanofibers by electrospinning. *Self-Assembled Nanomaterials I*: Springer; 2008. p. 107-71.
- Wendorff JH, Agarwal S, Greiner A. *Electrospinning: materials, processing, and applications*. John Wiley & Sons; 2012.
- Yoo HS, Kim TG, Park TG. Surface-functionalized electrospun nanofibers for tissue engineering and drug delivery. *Advanced drug delivery reviews*. 2009;61(12):1033-42.
- Beachley V, Wen X. Polymer nanofibrous structures: Fabrication, biofunctionalization, and cell interactions. *Progress in polymer science*. 2010;35(7):868-92.
- Homaeigohar S, Elbahri M. Nanocomposite electrospun nanofiber membranes for environmental remediation. *Materials*. 2014;7(2):1017-45.
- Pesetskii SS, Bogdanovich SP, Myshkin NK. Tribological behavior of nanocomposites produced by the dispersion of nanofillers in polymer melts. *Journal of Friction and Wear*. 2007;28(5):457-75.
- Nie G, Li Z, Lu X, Lei J, Zhang C, Wang C. Fabrication of polyacrylonitrile/CuS composite nanofibers and their recycled application in catalysis for dye degradation. *Applied Surface Science*. 2013;284:595-600.
- Fuenmayor CA, Lemma SM, Mannino S, Mimmo T, Scampicchio M. Filtration of apple juice by nylon nanofibrous membranes. *Journal of Food Engineering*. 2014;122:110-6.
- Homaeigohar SS, Buhr K, Ebert K. Polyethersulfone electrospun nanofibrous composite membrane for liquid filtration. *Journal of Membrane Science*. 2010;365(1):68-77.
- Homaeigohar SS, Elbahri M. Novel compaction resistant and ductile nanocomposite nanofibrous microfiltration membranes. *Journal of colloid and interface science*. 2012;372(1):6-15.
- Zheng Y, Cheng Y, Wang Y, Bao F, Zhou L, Wei X, et al. Quasicubic  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> nanoparticles with excellent catalytic performance. *The Journal of Physical Chemistry B*. 2006;110(7):3093-7.
- Wannatong L, Sirivat A, Supaphol P. Effects of solvents on electrospun polymeric fibers: preliminary study on polystyrene. *Polymer International*. 2004;53(11):1851-9.
- Ji L, Saquing C, Khan SA, Zhang X. Preparation and characterization of silica nanoparticulate-polyacrylonitrile composite and porous nanofibers. *Nanotechnology*. 2008;19(8):085605.

21. Zhang D, Karki AB, Rutman D, Young DP, Wang A, Cocke D, et al. Electrospun polyacrylonitrile nanocomposite fibers reinforced with Fe<sub>3</sub>O<sub>4</sub> nanoparticles: fabrication and property analysis. *Polymer*. 2009;50(17):4189-98.
22. Guo Z, Henry LL, Palshin V, Podlaha EJ. Synthesis of poly (methyl methacrylate) stabilized colloidal zero-valence metallic nanoparticles. *Journal of Materials Chemistry*. 2006;16(18):1772-7.
23. Ding B, Kim HY, Lee SC, Shao CL, Lee DR, Park SJ, et al. Preparation and characterization of a nanoscale poly (vinyl alcohol) fiber aggregate produced by an electrospinning method. *Journal of Polymer Science Part B: Polymer Physics*. 2002;40(13):1261-8.